



Aalborg Universitet

AALBORG UNIVERSITY  
DENMARK

## Functional Block Copolymers as Compatibilizers for Nanoclays in Polypropylene Nanocomposites

Jankova, Katja; Stribeck, Norbert; Zeinolebadi, Ahmad; Potarniche, Catalina-Gabriela; Jensen, Erik Appel; Christiansen, Jesper de Claville; Hvilsted, Søren

*Published in:*  
Nordic Polymer Days 2011

*Publication date:*  
2011

*Document Version*  
Early version, also known as pre-print

[Link to publication from Aalborg University](#)

*Citation for published version (APA):*

Jankova, K., Stribeck, N., Zeinolebadi, A., Potarniche, C-G., Jensen, E. A., Christiansen, J. D. C., & Hvilsted, S. (2011). Functional Block Copolymers as Compatibilizers for Nanoclays in Polypropylene Nanocomposites. In *Nordic Polymer Days 2011* KTH Mechanics, Royal Institute of Technology.

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

### Take down policy

If you believe that this document breaches copyright please contact us at [vbn@aub.aau.dk](mailto:vbn@aub.aau.dk) providing details, and we will remove access to the work immediately and investigate your claim.

# Functional Block Copolymers as Compatibilizers for Nanoclays in Polypropylene Nanocomposites

Katja Jankova<sup>1</sup>, Anders E. Daugaard<sup>1</sup>, Norbert Stribeck<sup>2</sup>, Ahmad Zeinolebadi<sup>2</sup>, Morteza Ganjaee Sari<sup>2</sup>, Catalina-Gabriela Potarniche<sup>3</sup>, Erik Appel Jensen<sup>3</sup>, Jesper de Claville Christiansen<sup>3</sup>, Søren Hvilsted<sup>1</sup>

Danish Polymer Centre, Department of Chemical and Biochemical Engineering, Technical University of Denmark, DK-2800 Kgs. Lyngby<sup>1</sup>


Institute for Technical and Macromolecular Chemistry, University of Hamburg, Bundesstr. 45, DE-20146 Hamburg<sup>2</sup>  
Department of Mechanical and Manufacturing Engineering, Aalborg University, DK-9220 Aalborg<sup>3</sup>

## Introduction

Nanoclays (NCI) possess a significant ion exchange capacity. Wetting of their naturally hydrophilic surface by the matrix polymer is undoubtedly a prerequisite for nanocomposites (NC) formation. Usually the NCI surface is rendered compatible with organic molecules by an onium exchange of the  $\text{Na}^+$  ions using hydrophobic surfactants like dimethyl dehydrogenated tallow ammonium ions.<sup>1</sup>


## Design, synthesis & characterization of a compatibilizer for MMT - PP nanocomposites

With the aim of creating tough nanocomposites (NC) [1] based on polypropylene (PP) and nanoclay (NCI) in the framework of the 7<sup>th</sup> EU program NANOTOUGH we have designed amphiphilic block copolymers utilizing Atom Transfer Radical Polymerization (ATRP) [2]. They consist of a hydrophobic block of Kraton L-1203 from Kuraray Co., Japan with molecular weight 7000 and PDI=1.05 (compatible with PP), and a hydrophilic block of quaternized dimethylaminoethyl methacrylate, DMAEMA (capable to perform the  $\text{Na}^+$  exchange):

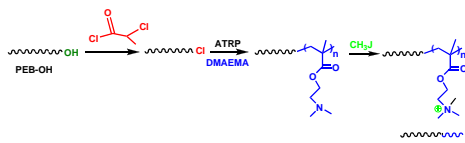


### Synthesis of quaternized PEB-b-PDMAEMA<sub>33</sub>N<sup>+</sup>

The size of the hydrophilic block was varied, which increasingly caused better dispersibility of the block copolymer in water. This was essential for the exchange of the  $\text{Na}^+$  ions of the used NCI (3.8 wt.-% aq. dispersion of montmorillonite, MMT from Laviosa Chimica Mineralia, Italy) by the synthesized charged block copolymer, which was performed in water. The modified MMT was then washed with water/ethanol until no  $\text{Na}^+$  was detected (0.1 M  $\text{AgNO}_3$ ) and freeze dried.

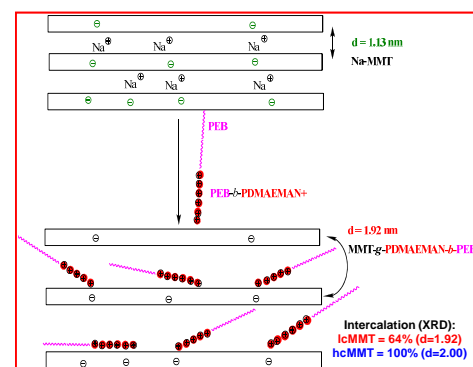


### Possible intercalation with the charged block copolymer

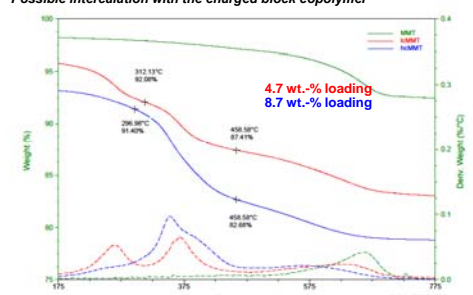

TGA overlay of freeze dried MMT, modified MMT with low (lc) and high content (hc) of the designed compatibilizer


## Abstract

Novel amphiphilic block copolymer has been designed, characterized and tested as a compatibilizer in PP-MMT nanocomposites in 2 different contents. SAXS has been used to monitor slow mechanical tests. The MMT acts like a nucleating agent to the PP that starts competitive nucleation of crystallites in the PP during manufacturing. Consequently, the PP crystallites in the composites are small and imperfect - the self-reinforcement of the PP is replaced by alien-reinforcement.




Simplified structural model for the semicrystalline structure of pure PP (left) and of the PP phase in the MMT nanocomposites (right). The thin vertical domains are drawn only to indicate that the composite contains MMT layers


## Stress relaxation

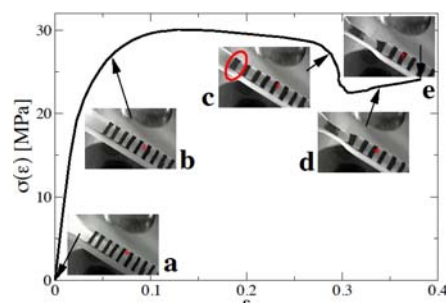

Stress relaxation and spot translation caused by necking in a true-stress curve  $\sigma(\epsilon)$  as a function of the local strain  $\epsilon$ . a: Start of test. The X-ray beam spot is indicated by a cross. b: Homogeneous stretching. Spot does not move. c: Necking has started (see ellipse). Material shows stress relaxation. d: Spot moving towards neck. e: End of testing.

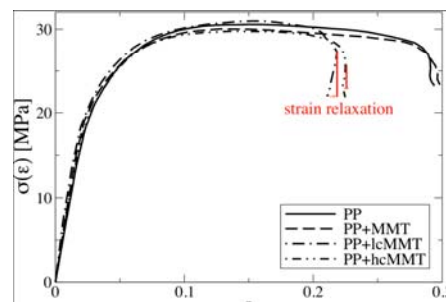


Tensile testing of PP/MMT nanocomposites. True stress  $\sigma(\epsilon)$  as a function of local strain  $\epsilon$  at the position of irradiation. Compatibilized materials exhibit even relaxation of local strain  $\epsilon$

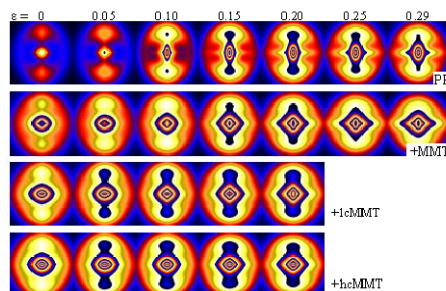


SAXS intensities  $I(s_{1,2}, s_3)$ , identical logarithmic scale, straining direction  $s_3$  (vertical),  $-0.15 \text{ nm}^{-1} \leq s_{1,2} \leq 0.15 \text{ nm}^{-1}$ . Full patterns ranging to  $0.25 \text{ nm}^{-1}$ .


## Nanostructure evolution

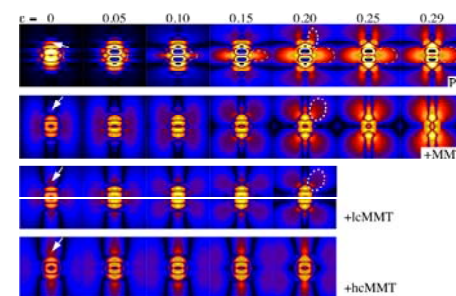

CDFs  $|z(y_{12}, y_3)|$  computed from SAXS, identical logarithmic scale, straining direction  $y_3$  (vertical),  $-60 \text{ nm} \leq y_{12}, y_3 \leq 60 \text{ nm}$

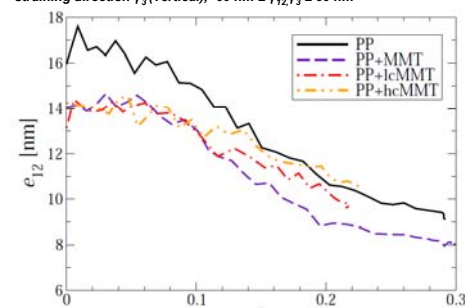

Nanostructure evolution during tensile testing of PP nanocomposites determined from the CDF long-period peak. Average lateral extension  $e_{12}$  of the crystalline PP domains as a function of the local macroscopic strain  $\epsilon$  in the irradiated volume

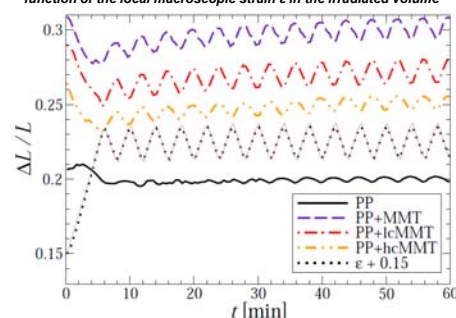

Nanostructure evolution during load cycling of PP nanocomposites determined from the CDF long-period peak. Relative standard deviation  $\Delta L/L$  of the long period distribution as a function of the elapsed time. Additionally the local macroscopic strain  $\epsilon(t)$  is shown

## Conclusions

- Novel block copolymer has been designed and tested as compatibilizer for PP/MMT nanocomposite.
- Missing improvement of the tensile properties appears to result predominantly from the inhibition of a load-bearing semicrystalline morphology inside the PP by the MMT.
- From the respective half-lives we have for the first time assessed the reinforcement of the composite and the weakening of the PP.

## Acknowledgments

This work has been supported by the 7<sup>th</sup> framework program of the European Union (Project NANOTOUGH FP7-NMP-2007-LARGE). Kuraray Co., Ltd. Elastomer Division, Japan is acknowledged for providing Kraton L-1203; Z. Vuluga and Mr. Radovici from ICECHIM CP, Romania for the XRD analyses. The authors thank the Hamburg Synchrotron Radiation Laboratory (HA-SYLAB) for beam time granted in the frame of projects IL-2008-0015 and IL-2011-0087.

## References

- [1] B. Chen, J.R.G. Evans. *Soft matter* **2009**, 5, 3572-3584.
- [2] K. Jankova, X. Chen, J. Kops, W. Batsberg. *Macromolecules* **1998**, 31, 538-541; *Macromol. Rapid Commun.* **1999**, 20, 219-223.
- [3] A.D. Drozdov, A.-L. Hog Leire, J. de C. Christiansen. *Composites Science and Technology* **2009**, 69, 2596-2603.
- [4] N. Stribeck, U. Nöchel, S. S. Funari, T. Schubert, A. Timmann. *Macromol. Chem. Phys.* **2008**, 209, 1992-2002.